



FOOD TECHNOLOGY FACT SHEET

Adding Value to OKLAHOMA

405-744-6071 • www.fapc.biz • fapc@okstate.edu

December 2018

Green Composite Panels Manufactured from Eastern Redcedar

Salim Hiziroglu

FAPC Wood Products Specialist

Wood-base composite panels including particleboard and fiberboard are widely used for many applications, such as underlayment for carpeting as core material, paneling, furniture and cabinet manufacture. The majority of particleboard panels is produced using 10 to 15 percent formaldehyde-based adhesives primarily urea formaldehyde (UF) as a binder for typical production. This fact sheet summarizes some of the main aspects of particleboard manufactured from Eastern redcedar using non-toxic modified starch as green binder.

It is a known fact formaldehyde-based adhesives are considered as a dangerous substance due to formaldehyde emission and linked to health problems from both short- and long-term exposure. Therefore, there is a movement to find alternative green adhesives that eliminate formaldehyde emission from the panels. Modified starch is one such potential environmentally friendly binder.

Eastern redcedar (*Juniperus virginiana* L.) is considered an invasive species encroaching in the Great Plains and one of the predominant invasive woody species in the United States. Eastern redcedar quickly replaces the native grasslands, adversely influencing the diversity of plants, birds and small mammals in Oklahoma. With an estimated growing rate of 380 hectares per day resulting in a significant adverse impact on the overall ecological system. Negative impacts of the encroaching of Eastern redcedar include the loss of native plants and animals, reduction of forage production and livestock handling, impacts on soil hydraulic properties and increased risk of wildfires. As an invasive species Eastern redcedar could

Onur Ulker

Assistant Professor, Kirikkale University, Turkey

be considered as a viable raw material to manufacture particleboard panels

In a past study, experimental composite panels from whole-tree chipped redcedar were manufactured using UF adhesive, resulting in both satisfactory physical and mechanical properties. Since there is no or little information on properties of particleboard panels made from Eastern redcedar using modified starch, this study attempted to produce initial data on properties of such value-added panel products. When one considers the combination of this resource with a green-based adhesive, such invasive species can be converted into value-added panel products so an important ecological problem can be solved with an environmentally friendly approach.

Manufacture of Experimental Particleboard Panels Using Starch

Commercially produced Eastern redcedar particles supplied by a local producer in Oklahoma were used to produce experimental panels. Dried particles having a moisture content of 3 percent were classified into fine and coarse sizes on a 20-mesh and 60-mesh screen, respectively. Coarse particles were used for the core layer of the three-layer particleboard, while the fine particles were used for the surface layers of the panel. Corn starch, along with glutardialdehyde (GDA) was mixed manually with the particles as binder for the panels. GDA is a colorless, oily liquid organic compound having the formula of $\text{CH}_2(\text{CH}_2\text{CHO})_2$, which is widely used as a disinfectant agent for medical equipment.

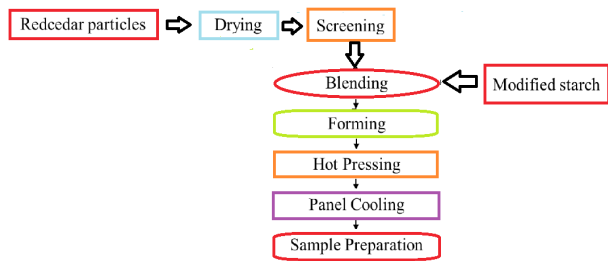


Figure 1. Flowchart of panel manufacture.



Figure 3. Dry and 24-h water soaked samples.



Figure 2. Untrimmed panel.

No wax or any other additives were used in production of the samples. The ratio of the surface layer thickness to the total thickness of a panel known as the shelling ratio was 0.30 for all specimens. Figures 1 and 2 illustrate the overall process of panel manufacture and untrimmed panel, respectively. Hand-formed mats were pressed in a computer-controlled press, an Erie Mill & Press Company Inc., 24-inch by 24-inch 270-ton press using a pressure of 5.5 MPa at a temperature of 180 degrees Celsius for 20 minutes. A total of 15 panels were made using each of the three density levels. Panels were conditioned in a conditioning room, having 65 percent relative humidity and a temperature of 20 degrees Celsius for two weeks before samples were cut for different tests based on American Society for Testing Material D1037-12.

Determination of Mechanical and Physical Properties of the Panels

The mechanical properties of the specimens, including bending strength and internal bond strength were carried out on a Comten Testing System, “Model 95-VD” equipped with 1000 kg load cell. Thickness swelling and water absorption tests were carried out on 100 mm by 100 mm by 12 mm size specimens by soaking in distilled water for 2 and 24 hours. Surface characteristics of 50 mm by 300 mm by 12 mm samples were evaluated by employing a fine stylus profilometer Hommel T-500 unit, having TkE model pick-up equipped with a skid type diamond stylus having 5 μm tip radius and

a 90-degree tip angle. The samples also were examined using a scanning electron microscope, FEI Quanta 600 FEG scanning electron microscope with an EVEX X-ray microanalysis system. The standard testing method for determining formaldehyde levels from wood products using a desiccator, ASTM D5582-14 was employed to examine to measure formaldehyde emission. The formaldehyde levels of the samples were determined by collecting air-borne formaldehyde in a small distilled water reservoir within a closed desiccator.

Initial Test Results of the Samples

Overall bending and internal bond strength of the samples were determined to be within the expected range as compared to those of typical commercially manufactured particleboard panels from other species. Modulus of elasticity and internal bond strength values of the samples ranged from 344,263 psi to 640.337 psi and 63 psi to 132 psi, respectively. Water absorption and thickness swelling of the panels were relatively high. Panels made with 0.80 g/cm³, 0.70 g/cm³ and 0.60 g/cm³ density levels had water absorption and values of 164 percent 160 percent and 153 percent, respectively. Corresponding thickness swelling values were 18 percent, 23 percent and 31 percent. Typical commercially manufactured particleboard would have within thickness swelling values of ranging from 8 to 10 percent as a result of a 24-hour water soaking test. The main reason of dimensional instability of the samples can be related to very large hygroscopicity of starch as well as not using any wax as additives in the samples. Figure 3 shows thickness swelling of dry and water soaked samples for comparison purpose. Also, nonhomogeneous mixture of starch, as illustrated in Figure 4 taken by scanning electron microscope, would result in low dimensional stability of the panels.

Further information can be found in below references:

ASTM International 2014. ASTM D5582-14 Standard Test Method for Determining Formaldehyde Levels from Wood Products Using a Desiccator. Retrieved from <https://doi.org/10.1520/D5582-14>.

ASTM International 2012. ASTM D1037-12 Standard Test Methods for Evaluating Properties of Wood-Base Fiber and Particle Panel Materials. Retrieved from <https://doi.org/10.1520/D1037-12>.

Chotikhun, A., and S. Hiziroglu. 2017. Some properties of composite panels manufactured from Eastern redcedar (*Juniperus virginiana* L.) using modified starch as a green binder. *Journal of Natural Fibers* doi: 10.1080/15440478.2016.1240642.

H'ng, P. S., S. H. Lee, Y. W. Loh, W. C. Lum, and B. H. Tan. 2011. Production of low formaldehyde emission particleboard by using new formulated formaldehyde based resin. *Asian Journal of Scientific Research* 4: 264-270.

Hiziroglu, S., and R. Holcomb. 2005. Some of the properties of three-layer particleboard made from Eastern redcedar. *Building and Environment* 40:719-723.

McKinley, D., and J. Blair. 2008. Woody plant encroachment by *Juniperus virginiana* in a mesic native grassland promotes rapid carbon and nitrogen accrual. *Ecosystems* 11: 454-468.

Moubarik, A., H. R. Mansouri, A. Pizzi, A. Allal, F. Charrier, M. A. Badia, and B. Charrier. 2013. Evaluation of mechanical and physical properties of industrial particleboard bonded with a corn flour-urea formaldehyde adhesive. *Composites: Part B* 44: 48-51.

Reddin, C. J., and D. C. Kremetz. 2016. Small mammal communities in Eastern redcedar forest. *The American Midland Naturalist* 175(1): 113-119.

Yang, Z., A. Kumar, R. L. Huhnke, M. Buser, and S. Capared. 2016. Pyrolysis of eastern redcedar: Distribution and characteristics of fast and slow pyrolysis products. *Fuel* 166: 157-165.

Yu, L., X. Liu, E. Petinakis, K. Dean, and S. Bateman. 2013. Chapter 4: Starch Based Blends Composites and Nanocomposites. *Advances in Natural Polymers, Composites and Nanocomposites*. Springer. Heidelberg, New York. pp. 121-154.

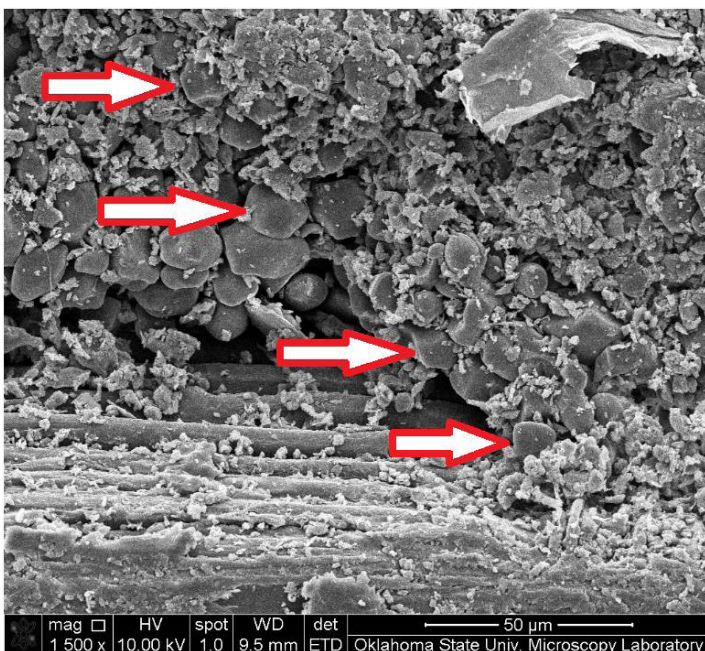


Figure 4. Scanning electron microscope showing distribution of starch particulars in the panels.

The Oklahoma Cooperative Extension Service Bringing the University to You!

The Cooperative Extension Service is the largest, most successful informal educational organization in the world. It is a nationwide system funded and guided by a partnership of federal, state, and local governments that delivers information to help people help themselves through the land-grant university system.

Extension carries out programs in the broad categories of agriculture, natural resources and environment; home economics; 4-H and other youth; and community resource development. Extension staff members live and work among the people they serve to help stimulate and educate Americans to plan ahead and cope with their problems.

Some characteristics of Cooperative Extension are:

- The federal, state, and local governments cooperatively share in its financial support and program direction.
- It is administered by the land-grant university as designated by the state legislature through an Extension director.
- Extension programs are nonpolitical, objective, and based on factual information.
- It provides practical, problem-oriented education for people of all ages. It is designated to take the knowledge of the university to those persons who do not or cannot participate in the formal classroom instruction of the university.
- It utilizes research from university, government, and other sources to help people make their own decisions.
- More than a million volunteers help multiply the impact of the Extension professional staff.
- It dispenses no funds to the public.
- It is not a regulatory agency, but it does inform people of regulations and of their options in meeting them.
- Local programs are developed and carried out in full recognition of national problems and goals.
- The Extension staff educates people through personal contacts, meetings, demonstrations, and the mass media.
- Extension has the built-in flexibility to adjust its programs and subject matter to meet new needs. Activities shift from year to year as citizen groups and Extension workers close to the problems advise changes.